

Letters

Anisotropy of the photo-elastic effect in Nd:KGd(WO₄)₂ laser crystals

P A Loiko¹, V G Savitski², A Kemp², A A Pavlyuk³, N V Kuleshov¹
and K V Yumashev¹

¹ Center for Optical Materials and Technologies, Belarusian National Technical University, 65/17 Nezavisimosti Ave., Minsk 220013, Belarus

² Institute of Photonics, University of Strathclyde, Wolfson Centre, 106 Rottenrow, Glasgow G4 0NW, UK

³ A V Nikolaev Institute of Inorganic Chemistry, Siberian Branch of Russian Academy of Sciences, 3 Lavrentyev Ave., Novosibirsk 630090, Russia

E-mail: kinetic@tut.by and vasili.savitski@strath.ac.uk

Received 18 January 2014, revised 17 February 2014

Accepted for publication 18 February 2014

Published 14 March 2014

Abstract

The anisotropy of thermal lensing and the photo-elastic effect is characterized for diode-pumped Nd:KGd(WO₄)₂ crystals cut along the N_p and N_g optical indicatrix axes and along its optical axis, $O = N_g + 43^\circ$, at a laser wavelength of 1067 nm. Distortions in the spatial profile of the output laser beam are analyzed. The thermal lens is astigmatic; the orientation of its principal meridional planes, A and B , is determined by the anisotropy of photo-elastic effect. The thermal lens has opposite signs for rays lying in the principal meridional planes for N_p - and O -cut crystals; it is positive for an N_g -cut crystal. The increase of thermal lens optical power after absorption of 1 W of pump power, i.e. the thermal lens sensitivity factors $M_{A(B)}$, and astigmatism degree $S = |M_A - M_B|$ are determined. The photo-elastic effect was found to increase the optical power of the thermal lens and was significant for all studied crystal orientations.

Keywords: double tungstates, diode-pumping, thermal lensing, photo-elastic effect

(Some figures may appear in colour only in the online journal)

1. Introduction

Nd- and Yb-doped potassium gadolinium tungstate, Nd:KGd(WO₄)₂ (KGW), is an attractive material for cw [1–4] and pulsed [5–8] low-threshold diode-pumped lasers operating in the vicinity of 1 and 1.3 μ m. KGW is a biaxial crystal, with three crystal orientations having been employed so far for laser engineering: along the b (N_p) axis [1–3, 5–8], along the N_g axis [9–12] and along the optical axis (O) [13, 14], i.e. $N_g + 43^\circ$ in the N_p – N_g plane [15]. Strong astigmatism of the thermo-optical properties of the material results in significant variation in the sign and value of the thermal lens in crystals cut for light propagation along the N_p and N_g axes under diode- or flash-lamp pumping [9, 12, 15, 16]. Thermal lens measurements

were reported previously for the N_p - and N_g -cut Nd:KGW crystals at the wavelength of 1.06 μ m under the flash-lamp pumping [9, 15, 16] and at the wavelength of 1.35 μ m under the diode pumping [12].

O -cut KGW laser crystals have recently attracted significant attention due to the so-called ‘conical refraction’ effect [17]. This effect is thought to be responsible for polarization tuning of the laser emission [13], and the ‘excellent’ laser beam quality [14] in Nd:KGW lasers using this crystal cut. However, to the best of our knowledge, thermo-optical properties of the O -cut KGW crystal have never been taken into account when analyzing conical refraction effects in these lasers.

In this letter we present for the first time the results of experimental and theoretical analysis of thermal lens in the

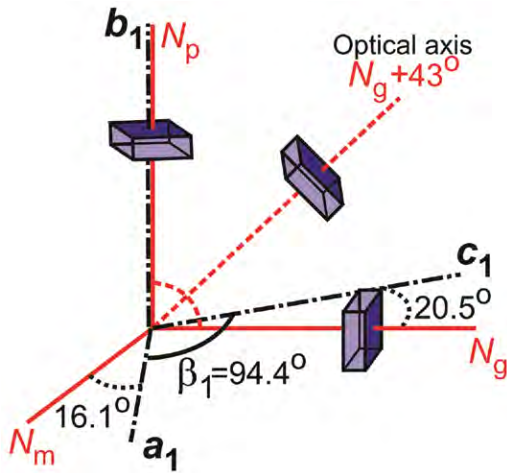


Figure 1. Orientation of studied Nd:KGd(WO₄)₂ laser crystals with respect to axes of optical indicatrix (N_p , N_m , N_g) and crystallographic axes (a_1 , b_1 , c_1 – $I2/c$).

diode-pumped Nd:KGW laser with the crystal cut for light propagation along the optical axis (the so-called ‘conical refraction laser’). A direct comparison of thermal lens properties under identical experimental conditions is made for Nd:KGW lasers with crystals cut along the N_p and N_g axes of optical indicatrix. It was found that, as has been reported in Nd:YLF [18], the photo-elastic effect and its anisotropy in KGW affects the sign and value of the thermal lens in the crystal. The contribution of the photo-elastic effect to the thermal lens at $1\mu\text{m}$ was calculated for three orientations of the Nd:KGW crystal.

2. Experimental details

KGW crystals with Nd ion concentration of 3at% were grown by the technique described in [19]. Three different crystal orientations were studied, namely N_p -, N_g - and O -cut (figure 1). The crystal thickness was 1 mm and the aperture was $3\times 3\text{mm}^2$.

The thermal lens in diode-pumped Nd:KGW laser crystals was characterized by analyzing changes in the spatial profile of the output laser beam (figure 2). For cw pumping, a fiber-coupled AlGaAs laser diode producing unpolarized emission was used ($\lambda_p = 810\text{nm}$, FWHM $\sim 3\text{nm}$). Pump radiation was focused into the laser crystal by a pair of spherical lenses (collimating lens, CL, and focusing one, FL). The radius of the pump beam ω_p inside the crystals was measured to be $180\mu\text{m}$. Pump absorption in all the Nd:KGW crystals under study was measured directly using the pump laser diode emission to be more than 97%. The input and output faces of the crystals were anti-reflection (AR) coated for the pump and laser (1067 nm) wavelengths. The crystals were kept in thermal contact with a copper heat-sink by means of heat grease; its temperature was maintained at $\sim 17^\circ\text{C}$.

The laser cavity was formed by a concave HR@1067 nm mirror ($R = 50\text{mm}$, HT@810 nm) and a flat output coupler, OC ($T = 0.5\%$ @1067 nm). The air gap between the crystal and the HR mirror was 13 mm; the total cavity length was 47 mm. The

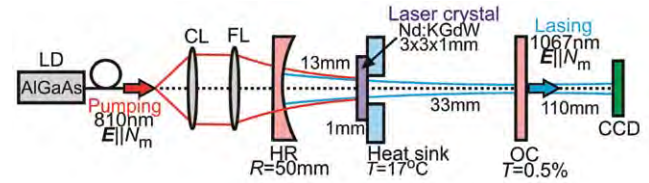


Figure 2. Experimental set-up for thermal lens measurements in Nd:KGd(WO₄)₂ laser crystal.

radius of the TEM₀₀ cavity mode in the laser crystals was calculated by the ABCD method to be $\sim 180\mu\text{m}$. The polarization of the output beam was naturally selected by the anisotropy of the laser gain (it was $E\parallel N_m$ for N_p - and N_g -cut crystals). For the O -cut crystal near the threshold, the orientation of the vector of polarization was very sensitive to the pump power (the similar behavior was observed previously in [13] for O -cut Yb-doped KGW). However, at higher pump levels the laser polarization stabilized to $E\perp N_m$. The output beam was near-Gaussian with the $M^2 < 1.1$. This M^2 value was found to be unchanged within the pump powers used in the experiments. The spatial profile of the output beam at a distance of 11 cm from the OC was measured using a CCD camera. The second moment diameter of the beam was measured.

Significant astigmatism of the thermal lens in KGW crystals was reported in [9, 12]. This means that the laser output beam is, in general, elliptical. That is why the measurements of the laser beam sizes were performed along the principal meridional planes A and B , i.e. planes which correspond to major and minor semi-axes of these ellipses. The dependence of the radii of the laser beam $\omega_{A(B)}$ along directions A (B) on the absorbed pump power P_{abs} was measured. The optical power of the thermal lens $D_{A(B)}$ and the sensitivity factor, $M_{A(B)} = dD_{A(B)}/dP_{\text{abs}}$ can then be calculated from the laser resonator parameters by the ABCD method [12, 20]. The sensitivity factor shows the increase of the thermal lens optical power on absorption of 1 W of pump power. The difference $S = |M_A - M_B|$ is called the astigmatism degree (for a spherical thermal lens $S = 0$). The orientation of A and B planes, $M_{A(B)}$ and S values make the complete set of thermal lens parameters.

3. Results

Typical spatial profiles of the output beam of the Nd:KGW lasers captured with the CCD camera are presented in figure 3. Here the upper and lower images correspond to the low and high values of absorbed pump power of $P_{\text{abs}} = 0.1$ and 0.5 W. The profiles are near-circular for low pump level (near the laser threshold). With increase of the pump power, the profiles become elliptical.

The measured dependencies of the output beam radii, $\omega_{A(B)}$, on the absorbed pump power, P_{abs} , are shown in figure 4. Here the points are the experimental data; curves are the results of modeling with the ABCD method. For the N_p - and O -cut crystals, the thermal lens results in expansion of the laser beam along the A direction and in its compression in orthogonal B direction. In contrast, for the N_g -cut crystal the thermal lens leads to expansion of the laser beam along both A and B directions.

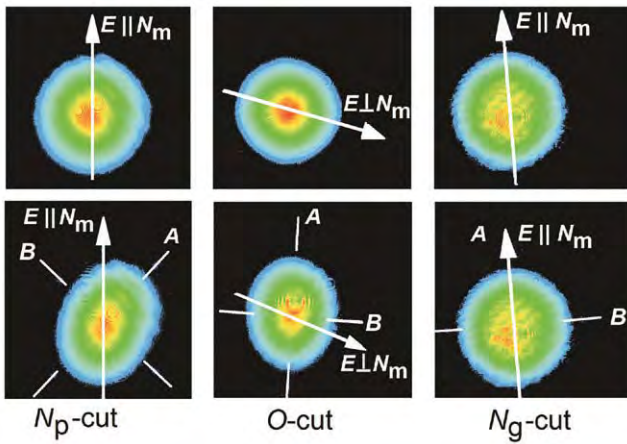


Figure 3. Spatial profiles of the output beam of a diode-pumped Nd:KGd(WO₄)₂ laser based on N_p-, N_g- and O-cut crystals; upper and lower images correspond to low and high pump levels.

In general, the orientation of the A and B planes is not directly related with polarization of the laser emission. Indeed, for the N_p-cut crystal, the A (B) directions make the angle of ~30° with the N_m (N_g) axes; for the O-cut crystal, they make the angle ~25° with the N_m (⊥N_m) axes; and for the N_g-cut crystal, A||N_m and B||N_p. The scheme illustrating this difference is presented in figure 5 (circles and ellipses correspond to spatial profiles of the output beam at low and high pump levels).

It was demonstrated recently that the orientation of principal meridional planes for the flash-lamp-pumped Nd:KGdW crystal is determined by the anisotropy of the thermal expansion [15]. According to our data, this is also true for the diode pumping. Indeed, maximum and minimum values of the thermal expansion coefficient in the N_m-N_g plane correspond to the X'₁ and X'₃ principal axes, with N_m^X'₁= 32.1° [21]. This is in agreement with our data, A^N_m ~ 33°. As a result, for the N_p-cut crystal, A||X'₁ and B||X'₃. For the O-cut crystal, directions with max and min thermal expansion are

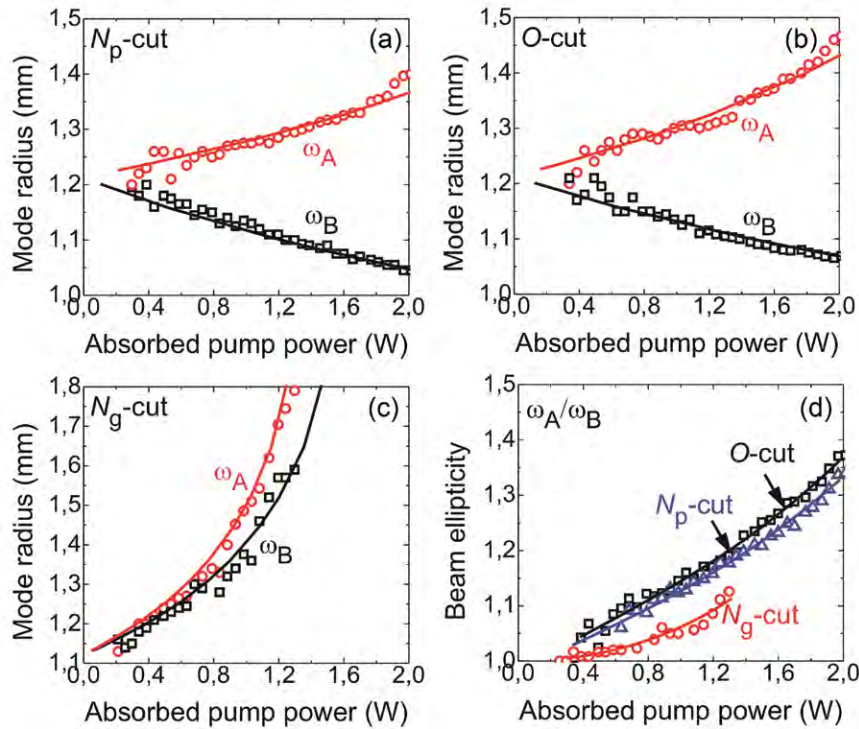


Figure 4. Radii of the TEM₀₀ laser mode, $\omega_{A(B)}$, as a function of the absorbed pump power for N_p-cut (a), O-cut (b) and N_g-cut (c) Nd:KGd(WO₄)₂ crystals; (d) beam ellipticity ω_A/ω_B .

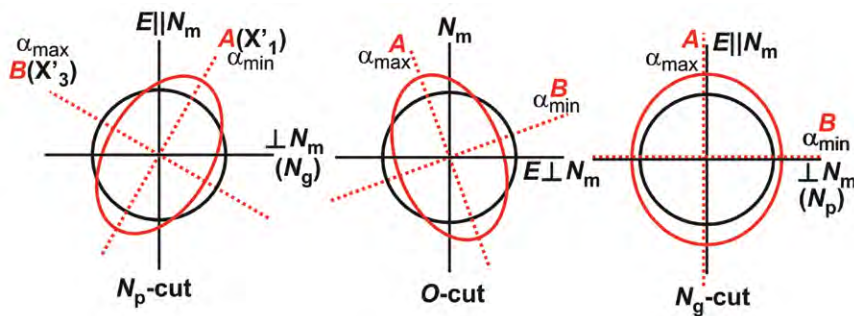


Figure 5. Distortion of the output beam of the Nd:KGd(WO₄)₂ laser due to the influence of the thermal lens: black circles and red ellipses correspond to beam profiles at low and high pump levels, dotted lines correspond to principal meridional planes (A and B directions).

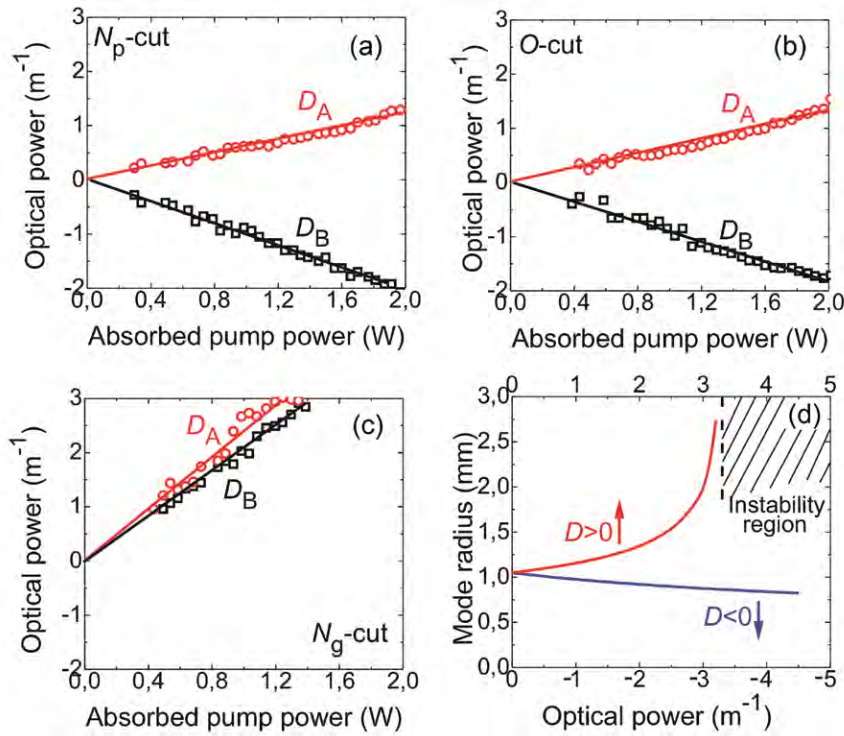


Figure 6. Optical power of the thermal lens along principal meridional planes, $D_{A(B)}$, as a function of the absorbed pump power for N_p - (a), O - (b) and N_g -cut (c) Nd:KGd(WO₄)₂ crystals; (d) ABCD modeling of the output mode of the Nd:KGd(WO₄)₂ laser.

rotated by $\sim 30^\circ$ -anticlockwise from the N_m ($\perp N_m$) axes which is again in agreement with our data. Maximum and minimum values of the thermal expansion coefficient in the N_m - N_p plane (N_g -cut crystal) correspond directly to N_m and N_p axes. This also agrees with the observed coincidence of A and B directions with N_m and N_p axes (figure 3).

The ratio of the radii of an elliptical Gaussian beam, ω_A/ω_B , is denoted as the beam ellipticity, see figure 4(d). It increases monotonically with the increase of the pump power. For the N_p - and O -cut crystals, the beam ellipticity reaches ~ 1.2 at $P_{\text{abs}} = 1$ W. The N_g -cut crystal allows one to obtain lower distortion of the output laser beam (as the corresponding value of the beam ellipticity is less than 1.1).

The calculated dependencies of the optical powers of the thermal lens in the two meridional planes, D_A and D_B , on the absorbed pump power are presented in figures 6(a)–(c). ABCD modeling of the laser resonator used (figure 6(d)) indicates that expansion (compression) of the output laser beam corresponds to the positive (negative) thermal lens in Nd:KGW crystal. Moreover, the value of ω is more sensitive to a positive lens. Thus, for the N_p - and O -cut crystals, the thermal lens is positive (negative) for rays lying in the A (B) planes; it is positive for rays lying in all meridional planes for the N_g -cut crystal. These findings are supported by the previous results reported for the N_p - and N_g -cut Nd:KGW crystals under the flash-lamp and diode pumping [9, 12, 15, 16].

The slopes of the dependencies in figures 6(a)–(c) are called thermal lens sensitivity factors, $M_{A(B)} = dD_{A(B)}/dP_{\text{abs}}$. These values are summarized in table 1. The difference of principal sensitivity factors is denoted as astigmatism degree, $S = |M_A - M_B|$. For the N_p -cut and O -cut crystals, the values

Table 1. Parameters of thermal lens for Nd:KGd(WO₄)₂ crystals at $1 \mu\text{m}$.

Parameter	Crystal cut		
	N_p -cut	O -cut	N_g -cut
$M = dD/dP_{\text{abs}}$ (Along A)	+0.57	+0.72	+2.35
$(\omega_p=180 \mu\text{m}), (m^{-1} W^{-1})$ (Along B)	-1.03	-0.92	+2.18
$S = M_A - M_B (m^{-1} W^{-1})$	+1.60	+1.64	+0.17

of S are close and equal to $\sim 1.6 m^{-1} W^{-1}$. In contrast, the N_g -cut crystal offers near eight times reduced astigmatism, $S \sim 0.2 m^{-1} W^{-1}$.

4. Discussion

Formation of the thermal lens in solid-state lasers is determined by three main effects, namely (i) the temperature variation of refractive index dn/dT , (ii) the photo-elastic effect (dependence of refractive index on thermally induced stress, P_{PE}) and (iii) the bulging of crystal end faces due to non-uniform thermal expansion Q_{dist} [22]. These contributions are summarized in the so-called ‘generalized’ thermo-optic coefficient [23], $\Delta = dn/dT + P_{PE} + Q_{\text{dist}}$. For diode pumping of bulk crystals (plane stress approximation), optical power of the thermal lens can be determined as [23]

$$D = \frac{P_{\text{abs}} \eta_h}{2\pi\omega_p^2 \kappa} \left(\frac{dn}{dT} + P_{PE} + Q_{\text{dist}} \right) \quad (1),$$

where η_h is the fractional head load (for Nd³⁺ ions, it is usually estimated as the quantum defect, $1 - \lambda_p/\lambda_l$, where λ_p and λ_l

Table 2. Thermo-optical parameters of Nd:KGW crystal at 1 μm (corresponding references are shown in square brackets).

Cut	n [29]		dn/dT (10^{-6} K^{-1}) [35]		α (10^{-6} K^{-1}) [20]			κ ($\text{W m}^{-1} \text{ K}^{-1}$) [26]
	$E \parallel N_m$	$E \perp N_m$	$E \parallel N_m$	$E \perp N_m$	α	α_{max}	α_{min}	
N_p	2.01	2.06 ($E \parallel N_g$)	-11.7	-17.7 ($E \parallel N_g$)	1.7	20.6	7.6	3.4
O		2.01		-16.6 ^a	9.8 ^a	14.2 ^a	5.9 ^a	2.7 ^a
N_g		1.98 ($E \parallel N_p$)		-15.9 ($E \parallel N_p$)	16.9	11.3	1.7	2.9

^a Results obtained in this paper.

are the pump and laser wavelengths, correspondingly); ω_p is the pump spot radius (top-hat profile); κ is the thermal conductivity. It should be noticed that in previous publications on the thermal lens in cubic $\text{Y}_3\text{Al}_5\text{O}_{12}$, the Q_{dist} term was evaluated as $(n-1)(1+\nu)\alpha$, where ν is the Poisson ratio, n is the refractive index and α is the thermal expansion coefficient in the direction of light propagation [22]. However, for KGW crystal the tensor of elastic constants C_{ij} is highly anisotropic and does not satisfy basic relations for high-symmetry materials like $\text{Y}_3\text{Al}_5\text{O}_{12}$ (even in rough approximation) [24], that is why the bulging of crystal end faces is described in KGW as $Q_{\text{dist}} = (n-1)\alpha$. Thermal conductivity κ is a scalar quantity for isotropic materials. However, for crystals with low anisotropy of thermal conductivity like double tungstates, a directionally averaged value of κ can be used [23]. Under longitudinal diode pumping, heat flow in the crystal is predominantly transverse. Thus, κ should be averaged over the plane perpendicular to the light propagation direction.

To date, the thermal conductivity for $\text{KGd}(\text{WO}_4)_2$ has been measured only for a few directions in the crystal [25, 26]. Complete characterization of the κ tensor has been performed for another representative of double tungstates, isostructural $\text{KLu}(\text{WO}_4)_2$ [27]. Since the thermal properties within this crystal family are very similar, we can use this data in the present paper. Directionally averaged values of κ for N_p -, O - and N_g -cut crystals are summarized in table 2.

The so-called thermal coefficient of the optical path $W = dn/dT + (n-1)\alpha$ was measured in this study at 1064 nm in the O -cut Nd:KGW crystal for $E \perp N_m$ by the beam deviation method [28] under the homogeneous heating to be $-(7 \pm 1) \times 10^{-6} \text{ K}^{-1}$. The W -coefficient for the O -cut Nd:KGW can also be calculated from known values of the thermo-optic coefficient dn_O/dT , index of refraction n_O and thermal expansion α_O . In general, the index of refraction $n(E \perp N_m)$ of a KGW crystal cut for light propagation in the N_p - N_g plane can be calculated as [29]

$$n(E \perp N_m) = \frac{n_g n_p}{(n_g^2 \cos^2 \phi + n_p^2 \sin^2 \phi)^{1/2}} \quad (2),$$

with the dn/dT ($E \perp N_m$) being, after differentiation,

$$\frac{dn}{dT}(E \perp N_m) = \frac{dn_g}{dT} \frac{n^3}{n_g^3} \sin^2 \phi + \frac{dn_p}{dT} \frac{n^3}{n_p^3} \cos^2 \phi \quad (3),$$

where n_g (n_p) and dn_g/dT (dn_p/dT) are the indices of refraction and thermo-optic coefficients, respectively, for $E \parallel N_g$ (N_p), and ϕ is the angle between the N_g axis and the direction of light propagation in the N_p - N_g plane ($\phi = 43^\circ$ in KGW crystal cut along the optical axis). The set of thermo-optical parameters of Nd:KGW at 1 μm is summarized in table 2. The index of

refraction in the O -cut crystal does not depend on polarization, i.e. $n_O(E \perp N_m) = n_m = 2.01$ at 1067 nm [30] at $\phi = 43^\circ$. The thermo-optic coefficient dn_O/dT does depend on polarization due to the different physical nature of these dependencies [31–33]. The value of the thermal expansion α_O along the optical axis can be calculated from the following expression [21]:

$$\alpha_O = \alpha_g \cos^2 \phi + \alpha_p \sin^2 \phi \quad (4),$$

where α_g and α_p are the thermal expansion coefficients along the g and p axes (see table 2 for values). The thermo-optic and thermal expansion coefficients calculated from equations (3) and (4) of the O -cut Nd:KGW at 1067 nm are shown in table 2. Therefore, the thermal coefficients of the optical path along the optical axis in Nd:KGW crystal are

$$W_O(E \perp N_m) = \frac{dn_O}{dT}(E \perp N_m) + [n_m - 1]\alpha_O = -6.7 \times 10^{-6} \text{ K}^{-1}$$

and

$$W_O(E \parallel N_m) = \frac{dn_m}{dT} + [n_m - 1]\alpha_O = -1.7 \times 10^{-6} \text{ K}^{-1}.$$

The calculated value of $W_O(E \perp N_m)$ is in good agreement with the one measured in this study. Unfortunately, due to thermal fracture of the O -cut crystal, the measurements of the W factor for $E \parallel N_m$ could not be performed and compared with the calculated value, but we believe our calculations are likely to agree well with experiment.

Thus, from equation (1) it is possible to evaluate the contribution of the photo-elastic effect P_{PE} to the overall thermally induced refraction in diode-pumped Nd:KGW without use of the corresponding photo-elastic coefficients, p_{ijkl} . This is carried out for the diode-pumped anisotropic crystal for the first time, to our knowledge. The results are summarized in table 3. Here three principal contributions are collected, namely dn/dT , P_{PE} and Q_{dist} , together with the overall value of Δ . It should be noted from our results that the photo-elastic contribution increases for both meridional planes A and B as the crystal orientation (cut) changes counter-clockwise from being along N_g to along the N_p axis (see figure 1). In N_g - and O -cut crystals the maximum (minimum) photo-elastic effect is observed along the direction with the maximum (minimum) value of thermal expansion coefficient α . In contrast, for the N_p -cut Nd:KGW the maximum (minimum) photo-elastic effect is observed along the direction with the minimum (maximum) value of thermal expansion coefficient α (see table 2 for the values of $\alpha_{\text{max, min}}$ and figure 5 for orientation of thermal expansion axes for each crystal cut). In general, the photo-elastic coefficient is determined by the net action of stress (which is in general a tensor in KGW) and thermal expansion [34], and one should

Table 3. Contribution of the photo-elastic effect to thermal lens optical power in diode-pumped Nd:KGd(WO₄)₂.

Crystal	Contribution to optical power of thermal lens (10^{-6} K^{-1})			Δ (10^{-6} K^{-1})
	dn/dT	P_{PE}	Q_{dist}	
N_p -cut, $E \parallel N_m$	-11.7	+11.2 (A) +7.3 (B)	+1.8	+1.3 (A) -2.6 (B)
O -cut, $E \perp N_m$	-16.6	+8.5 (A) +4.4 (B)	+10.0	+1.9 (A) -2.2 (B)
$E \parallel N_m$	-11.7	>+1.7 (A) <+1.7 (B)	+10.0	Positive (A) [15] Negative (B) [15]
N_g -cut, $E \parallel N_m$	-11.7	+0.6 (A) +0.2 (B)	+17.0	+5.9 (A) +5.5 (B)

not expect a direct relation between the latter and the value of the photo-elastic effect.

The values of the P_{PE} term, to the best of our knowledge, have never been reported previously for any crystal orientation of Nd:KGW. For the N_p -cut Nd:KGW crystal, P_{PE} is positive and comparable in absolute value with dn/dT . As a result, the optical power of the thermal lens is determined by the opposite action of temperature- and stress-dependent variation of the refractive index. This leads to different signs of the thermal lens for rays lying in principal meridional planes. Substantial difference of P_{PE} values for these planes determines the large astigmatism of thermal lens. The impact of the Q_{dist} term is moderate (20% from $|dn/dT|$), mainly because of a small α_p value ($1.7 \times 10^{-6} \text{ K}^{-1}$).

For the O -cut crystal the impact of positive Q_{dist} becomes more significant, but still is not enough for the crystal to demonstrate positive thermal lensing along both A and B directions for $E \perp N_m$. In the case of $E \parallel N_m$ the net effect of dn/dT and Q_{dist} results in a relatively small value of the thermal coefficient of $-1.7 \times 10^{-6} \text{ K}^{-1}$. However, the photo-elastic effect in the general case should be different for different polarizations of light [16, 18]; therefore the values previously calculated for $E \perp N_m$ will not be valid for $E \parallel N_m$ and, strictly speaking, not only the value, but even the sign of the lens cannot be predicted from the data available in this study. However, our measurements of thermal lens in the O -cut Nd:KGW crystal in $E \parallel N_m$ configuration under the flash-lamp pumping shows that it is positive along direction A and negative along direction B [15]. This allows us to estimate the maximum and minimum values of the photo-elastic contribution to the thermal lens (see table 3) under the current pump conditions.

For the N_g -cut crystal, the photo-elastic effect also results in an increase of refractive index ($P_{PE} > 0$). However, the absolute value of P_{PE} is small (compared with the dn/dT and especially the Q_{dist} terms). Thus, the optical power of the thermal lens is mainly determined by the dominance of the positive Q_{dist} over the negative dn/dT term, and the thermal lens is positive. The small difference between the P_{PE} values for the A and B planes leads to small astigmatism.

Reduction of Δ to $dn/dT + (n-1)\alpha$ is acceptable only for N_g -cut Nd:KGW, but this approach will result in some underestimation of optical power of the thermal lens. In contrast, for N_p -cut and O -cut crystal, the P_{PE} term cannot be omitted if the thermo-optic effects are to be described correctly.

5. Conclusions

The contribution of the photo-elastic effect to the thermal lens in diode-pumped Nd:KGW lasers at $1 \mu\text{m}$ was calculated based on measurements of the output laser beam distortions for light propagation along the N_g , N_p and optical axes of the crystal for the first time, to the best of our knowledge. The photo-elastic contribution was found to be positive for all studied crystal orientations. It increases when the crystal cut changes counter-clockwise from being along the N_g axis to along the N_p axis. In the case of an optical axis-oriented Nd:KGW crystal and for light polarization along N_m , the minimum and maximum values of the photo-elastic contribution were evaluated for the positive and negative thermal lens, respectively.

References

- [1] Demidovich A A, Shkadarevich A P, Danailov M B, Apai P, Gasmi T, Gribkovskii V P, Kuzmin A N, Ryabtsev G I and Batay L E 1998 *Appl. Phys. B* **67** 11–5
- [2] Boulon G, Metrat G, Muhlstein N, Brenier A, Kokta M R, Kravchik L and Kalisky Y 2003 *Opt. Mater.* **24** 377–83
- [3] Kuleshov N V, Lagatsky A A, Shcherbitsky V G, Mikhailov V P, Heumann E, Jensen T, Dening A and Huber G 1997 *Appl. Phys. B* **64** 409–13
- [4] Kaminskii A A, Pavlyuk A A, Klevtsov P V, Balashov I F, Berenberg V A, Sarkisov S E, Fedorov V A, Petrov M V and Lyubchenko V V 1997 *Inorg. Mater.* **13** 482–3
- [5] Zolotovskaya S A, Savitski V G, Gaponenko M S, Malyarevich A M, Yumashev K V, Demchuk M I, Raaben H, Zhilin A A and Nejezchleb K 2006 *Opt. Mater.* **28** 919–24
- [6] Liu M, Liu J, Li L and Liu S S 2009 *Laser Phys. Lett.* **6** 437–40
- [7] Major A, Langford N, Graf T, Burns D and Ferguson A I 2002 *Opt. Lett.* **27** 1478–80
- [8] Brunner F et al 2000 *Opt. Lett.* **25** 1119–21
- [9] Yumashev K V, Savitski V G, Kuleshov N V, Pavlyuk A A, Molotkov D D and Protaseny A L 2007 *Appl. Phys. B* **89** 39–43
- [10] Loiko P A, Kisel V E, Kondratuk N V, Yumashev K V, Kuleshov N V and Pavlyuk A A 2013 *Opt. Mater.* **35** 582–5
- [11] Savitski V G, Birch R, Fraczek E, Kemp A J, Loiko P A, Yumashev K V, Kuleshov N V and Pavlyuk A A 2013 *Proc. CLEO/Europe and EQEC 2013 (OSA) (Munich, Germany, 12–16 May 2013)* p CA12_12
- [12] Loiko P A, Yumashev K V, Kuleshov N V, Savitski V G, Calvez S, Burns D and Pavlyuk A A 2009 *Opt. Express* **17** 23536–43

- [13] Hellstrom J, Henricsson H, Pasiskevicius V, Bunting U and Haussmann D 2007 *Opt. Lett.* **32** 2783–5
- [14] Abdolvand A, Wilcox K G, Kalkandjiev T K and Rafailov E U 2010 *Opt. Express* **18** 2753–9
- [15] Loiko P A, Yumashev K V, Kuleshov N V and Pavlyuk A A 2012 *Appl. Phys. B* **106** 881–6
- [16] Loiko P A, Yumashev K V, Kuleshov N V and Pavlyuk A A 2010 *Appl. Opt.* **49** 6651–9
- [17] Hamilton W R 1833 *Trans. R. Irish Acad.* **17** 1–144
- [18] Zelenogorskii V V and Khazanov E A 2010 *Quantum Electron.* **40** 40–4
- [19] Loiko P A, Yumashev K V, Kuleshov N V and Pavlyuk A A 2012 *Appl. Phys. B* **106** 663–8
- [20] Hodgson N and Weber H 2005 *Laser Resonators and Beam Propagation. Fundamentals, Advanced Concepts, Applications* (New York: Springer)
- [21] Loiko P A, Yumashev K V, Kuleshov N V, Rachkovskaya G E and Pavlyuk A A 2011 *Opt. Mater.* **34** 23–6
- [22] Koechner W 2006 *Solid-State Laser Engineering* (New York: Springer)
- [23] Chenais S, Druon F, Forget S, Balembois F and Georges P 2006 *Prog. Quantum Electron.* **30** 89–153
- [24] Mazur M M, Velikovskii D Y, Kuznetsov F A, Mazur L I, Pavlyuk A A, Pozhar V E and Pustovoit V I 2012 *Acoust. Phys.* **58** 658–65
- [25] Biswal S, O'Connor S P and Bowman S R 2005 *Appl. Opt.* **44** 3093–7
- [26] Mochalov I V 1997 *Opt. Eng.* **36** 1660–9
- [27] Silvestre O et al 2008 *Opt. Express* **16** 5022–34
- [28] Vatnik S, Pujol M C, Carvajal J J, Mateos X, Aguiló M, Díaz F and Petrov V 2009 *Appl. Phys. B* **95** 653–6
- [29] Hernández-Rodríguez C and Frago-López A B 2014 *Opt. Laser Technol.* **55** 1–5
- [30] Pujol M C, Rico M, Zaldo C, Sole R, Nikolov V, Solans X, Aguiló M and Diaz F 1999 *Appl. Phys. B* **68** 187–97
- [31] Antoncik E 1956 *Czechoslovakij Fiz. Z.* **6** 209–16
- [32] Tsay Y F, Bendow B and Mitra S S 1973 *Phys. Rev. B* **8** 2688–96
- [33] Ghosh G and Palik E 1998 *Handbook of Thermo-Optic Coefficients of Optical Materials with Applications* (San Diego, CA: Academic)
- [34] Nye J F 1985 *Physical Properties of Crystals* (Oxford: Clarendon)
- [35] Loiko P A, Yumashev K V, Kuleshov N V, Rachkovskaya G E and Pavlyuk A A 2011 *Opt. Mater.* **33** 1688–94